



## Purpose and Application

Acid rain, bird droppings, fuel, antifreeze and many other environmental factors can damage automotive finishes. Especially in summertime, some substances can be very aggressive and cause severe damage. Therefore, automotive paint manufacturers as well as auto makers need to find out how different environmental phenomena will interact with a coating system.

For the development of stove enamel systems as well as for their quality testing it is of great importance to assess the temperature range and the max. temperature limit, respectively, where the components of the lacquer formulations (and thus also potentially the properties and the quality of the whole thing) begin to change.

The well-known main example for this are the yellowing of binding agents as well as the change in colour of pigments.

Concerning the subject of baked coatings within industrial production conditions, the accurate control of the corresponding processes is of crucial importance to achieve and continuously maintain/ guarantee the specified qualitative characteristics of the coating.

Due to different reasons, the actually existing conditions do not always correspond exactly to the preset process run which in the "worst case" may cause severely high non-conformity costs.

The **Gradient-oven 432 Smart** offers the possibility of a needs-based optimizing of the process for the product in question.

The „*actual* condition“ in the stove enameling production line, beforehand determined by means of an oven temperature recorder, can be simulated at the best via a requirement-orientated setting of an appropriate gradient and thus allows a nearly perfect 1:1 simulation of the respective stoving condition, however on the desired laboratory scale saving time and expenses.

## Principle of the Test

The **Gradient-oven 432 Smart**, is a testing instrument for the assessment of the baking and drying behavior of paint and powder coatings, resins, plastic materials and similar. The production process can be simulated by programming heat-up speed, baking temperature, and time.

The gradient-oven helps to speed up R & D projects saving time and money. The very good repeatability of measurements allows a remarkably accurate determination of the present limiting values.

Depending on the gradient-oven type coatings can be tested with temperatures up to 320 °C. By applying the coating system with a duplex frame applicator two different coating systems can be applied simultaneously on the same panel. This makes the comparison easier saving application time and material cost. In QC testing of baked coating systems the gradient-oven produces repeatable results many times faster than using traditional convection ovens.

In a standard test 5 different chemicals can be tested on one panel – e.g. H<sub>2</sub>SO<sub>4</sub> which simulates atmosphere and acid rain, NaOH for car wash detergents, pancreatine (bird dropping), brake fluid, and tree resin.

Liquid paints are applied with a film applicator and film application device. It is also possible to apply them by spraying, once the edges and reverse of the test panel have been masked. Powder coatings are applied electrostatically to either masked panels or panels covered with a magnetic strip. The panels are coated and baked under the specified processing conditions.



Application device

Panels (coated)

Using a pipette droplets (approx. 0.05 ml) of these various materials are placed at appropriate intervals on the test panel. Repeat this length down the panel with spacing about every 2 - 3 cm. The gradient-oven is then programmed to have a *linear gradient* in the range of 35 °C up to 80 °C.


## Execution

For evaluation the panels are thermally stressed and then washed under running water, dried and visually evaluated. The evaluation should be done after approx. one hour and again after 24 hours to see if any additional etching has occurred.


The temperature is documented at which the first visual changes and damages occurred.

The **Gradient-oven, Model 432 Smart**, is equipped with a microprocessor-controlled heating bench with 45 isolated heating elements, which produces a completely linear temperature gradient or step gradient.

"*Linear gradient*": means that a constant temperature is generated over the entire test panel. The linear gradient can be horizontal, i.e. the same temperature on both right and left sides of the test panel. However, a temperature can also be generated that is low on the left and high on the right with a maximum increase of 100 °C.

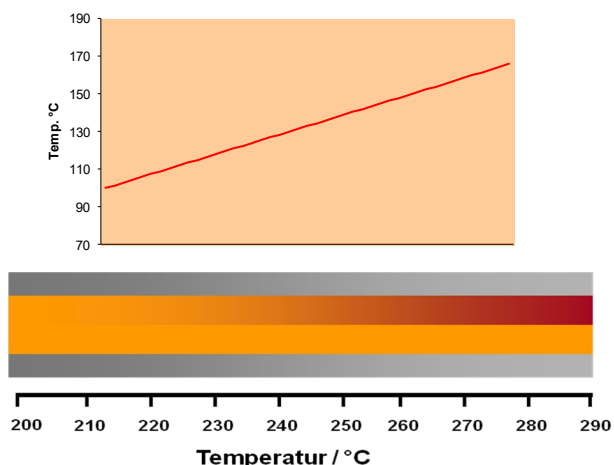

"*Step gradient*": 3 steps are offered to automatically divide the test panel into 2, 3 or 4 equal parts (temperature steps). Between each temperature step some heating elements are not heated to maintain the set value of each step. These elements are indicated in the report or the set temperature display at 23 °C.

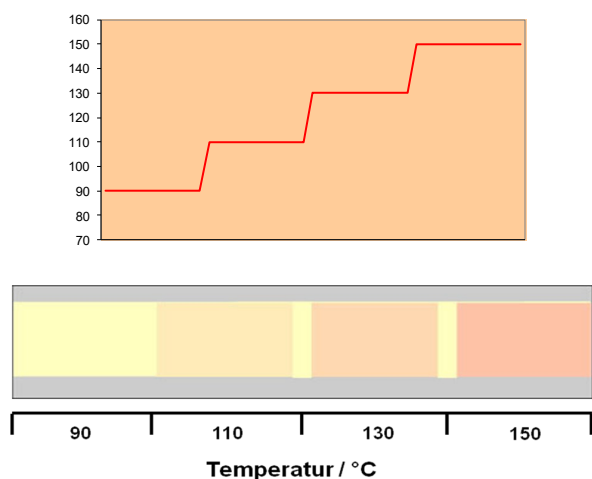

The **Gradient-oven, Model 432 Smart**, is a laboratory tabletop instrument, which can be placed in a non-hazardous area/room with normal room temperature (approx. 18 °C to 25 °C) and humidity (approx. <85%).

The operation and controlling are menu-guided in English, French or German via touch panel. All retrievable functions are displayed in the appropriate menu on the display.

The gradient-oven is equipped with two USB ports and one LAN connection (printer connection, data out). The scope of supply includes a special glass plate to insulate the area between the heating elements and test panel as well as particularly specified test panels.

For safety reasons, the **Gradient-oven 432 Smart** is equipped with a holding device for the test panels, which automatically transports the samples to be tested. A protective flap automatically closes the opening after inserting the test panels.

## Technical Data

Voltage	230 V, 50/60 Hz
Power Consumption	3400 VA
Heating Surface	520 x 100 mm (20.4 x 3.9 in)
Test Surface	500 x 70 mm (19.6 x 2.7 in)
Heating Elements	45 St.
Holding Device	reciprocates automatically (approx. 160 N) for insertion and removal of panel
Linear Gradient	max. temperature difference between 30 and 250(320) °C: 100 °C; 86 and 482 (608) °F: 180 °F
Step Gradient	with 2, 3 or 4 steps: max. temperature difference between two steps: 50 °C (90 °F)
Heat-Up-Speed	2 °C up to 30 °C/min, programmable (3,6 °F/min up to 54 °F/min)
Baking Time	in sec. and min.
Accuracy	control accuracy of the heating elements: < ± 2 °C (±3,6 °F) surface temperatures on 0.8 mm test panels from element 3 up to 43:  up to 200° ± 2 °C (up to 392 ° ± 3.6 °F)  up to 250 ° ± 3 °C (up to 482 ° ± 5.4 °F)  up to 320 ° ± 5 °C (up to 608 ° ± 9.0 °F)  Measured under specified test conditions
Dimensions (HxWxD)	approx. 470 x 860 x 585 mm (18 x 34 x 22 in)
Weight	approx. 103 kg

The right of technical modifications is reserved.  
TBE 432 Smart – VI/2022

Order Information	
Ord.-No.	Product-Description
03280131	<b>Gradient-Oven, Model 432 Smart I,</b> with an operating temperature of <b>30 °C up to 250 °C</b>
03280231	<b>Gradient-Oven, Model 432 Smart II,</b> with an operating temperature of <b>30 °C up to 320 °C</b>
	Includes <ul style="list-style-type: none"> <li>• Exhaust tube</li> <li>• Glass plate</li> <li>• Test panels (25 pcs.)</li> <li>• Marking strips (50 pcs.)</li> <li>• Operating Manual</li> </ul>

Accessories / Spare Parts	
Ord.-No.	Product-Description
08780132	Application device
08880132	Quadruple film applicator for the application device
08890132	Double-quadruple film applicator ( 2 chambers) for the application device
08820132	Template for powder
08830132	Test panels made of steel, for the application of specimens
08840132	Marking strips to mark the temperature range
08850232	Glass plate made of special glass